



PIPA

PLASTICS INDUSTRY
PIPE ASSOCIATION
OF AUSTRALIA LIMITED

INDUSTRY GUIDELINES POP020

Principles of polyethylene
(PE) electrofusion welding
and assessment

ISSUE 1.2 / MAY 2026



PRINCIPLES OF POLYETHYLENE (PE) ELECTROFUSION WELDING AND ASSESSMENT

1.0 INTRODUCTION

The purpose of this technical guideline is to provide insight into the principles of electrofusion (EF) welding and instruction on the assessment of fractographic features resulting from destructive testing. The objective of the electrofusion process is to achieve cohesion between a pipe and fitting by melting and fusing the two polyethylene surfaces together. Evidence of a satisfactory weld is demonstrated in the peel decohesion test by:

- a) tearing of the polyethylene, for example through the pipe or fitting wall or through the plane of the EF heating wires or;
- b) evidence of gross-ductility or micro-ductility at the pipe to fitting interface when separation occurs or;
- c) yielding of the pipe or fitting wall.

An unsatisfactory weld is one that lacks evidence of sufficient fusion (i.e., cohesion) across the pipe – fitting interface on completion of the peel decohesion test. In a failed specimen there is visible evidence of lack of fusion and/or voids over an excessive length of the fusion zone between the pipe and fitting.

This industry guideline applies to EF fittings manufactured in accordance with *AS/NZS 4129 Fittings for polyethylene (PE) pipes for pressure applications* that have been fused to PE pipes manufactured in accordance with *AS/NZS 4130 Polyethylene pipes for pressure applications*.

2.0 ELECTROFUSION WELDING PROCESS

A comprehensive description of the EF welding process is provided in PIPA's Industry Guidelines [POP001 Electrofusion Jointing of PE Pipes and Fittings for Pressure Applications](#) and [POP001A Guide to Electrofusion Assembly and Welding](#). POP001 provides best practice guidance for the safe and reliable electrofusion jointing of polyethylene (PE) pipe covering key fusion requirements, training and certification, tools and equipment, installation considerations, and post-fusion quality control. It should be read in conjunction with POP001A which provides step-by-step instructions for common installation methods such as socket assemblies, slip couplings and saddles. Reference should be made to these guidelines prior to performing EF welds.

3.0 PRINCIPLES OF ELECTROFUSION WELDING

EF welding requires application of an electric current for a defined period of time (fusion time) to resistance heating wires contained within the fitting. These wires are either embedded beneath the internal surface of the fitting (Figure 1) or exposed at the internal surface of the fitting (Figure 2).



Figure 1 – Inner wall of electrofusion coupler with embedded wire design.

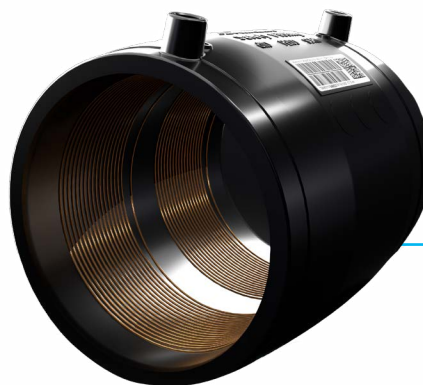


Figure 2 – Inner wall of electrofusion coupler with exposed wire design.

Image courtesy of Aliaxis

Heat generated in the wires raises the temperature of the surrounding PE material above the crystalline melting point. At either end of the heating zone the molten PE solidifies first (in regions known as “cold zones”), creating a cavity within which the PE melt is constrained. The expanding PE creates pressure within the cavity so that fusion takes place between the pipe and fitting interfaces.

The colour indicators or fusion indicator pins on the fittings will become visible if the required pressure has been created. Once the fusion time has elapsed, the joint assembly is left to cool undisturbed for a set time (cooling time). This cooling phase is critical to ensuring good, strong joints.

4.0 CRITICAL FACTORS FOR SUCCESSFUL FUSION

Good fusion results in cohesion at the interface leading to high strength and ductility between the pipe and EF fitting. This forms a common over-structure, created by co-crystallisation of the macromolecules beyond the weld interface.

Critical factors for achieving good fusion are outlined in Table 1. Fusion energy, power, temperature, and time are defined by the fitting manufacturer for each size and type of fitting. Fusion times and voltage are encoded into the fittings barcode which is read by the control box. Where a portable electric generator is used, it must have suitable capacity for welding the fitting. Good fusion is also highly dependent on using appropriately calibrated and maintained equipment and following the correct procedures for joint preparation and cleanliness.

Table 1 Critical factors for achieving good fusion in addition to joint preparation

CRITICAL FACTOR	DESCRIPTION	COMMENTARY
Fusion energy and power	Energy required to melt the polymer for a specified fusion time.	Specified by the fitting manufacturer. Power supply quality is important.
Fusion temperature	Melting, polymer expansion and molecular mobility driving diffusion and molecular entanglement.	Specified by the fitting manufacturer but can be influenced by quality of the power supply and control box maintenance.
Fusion time	Development of the correct temperature profile at the joint interface to achieve the above.	Specified by the fitting manufacturer.
Fusion/melt pressure	Melt pressure across the entire interface must be achieved for diffusion to occur.	Influenced by joint preparation, cleanliness, and assembly
Cooling time	Diffusion of molecular chains creating co-crystallisation of macromolecules beyond the weld interface are locked in either side of the joint.	Critical to ensuring joint strength and ductility.

Note: For more details on these critical factors including joint preparation refer to [PIPA POP001 – Electrofusion Jointing of PE Pipes and Fittings for Pressure Applications](#) and [PIPA POP001A Guide to Electrofusion Assembly and Welding](#).

5.0 TEST METHODS FOR ASSESSING ELECTROFUSION WELDS

There are several published methods for assessing EF weld quality. The primary test method referenced in AS/NZS 4129 – *Fittings for polyethylene (PE) pipes for pressure applications* is the peel decohesion method ISO 13954 *Plastics pipes and fittings – Peel decohesion test for polyethylene (PE) electrofusion assemblies of nominal outside diameter greater than or equal to 90 mm*. The test method has two distinct phases:

- The first involves preparation and destructive testing of the test pieces.
- The second phase is an assessment of the result. In particular, whether fitting – pipe interface fusion or cohesion has been achieved across a minimum length of heating zone area.

Note: Where fracture occurs at the fusion interface, the EF fitting side of the test piece shall be assessed for the percentage of brittle decohesion. Typically, matching fractographic features will be observed on both pipe and fittings sides of the fracture zone.

This is a destructive test method, where the test pieces are always taken to destruction. ISO 13954 (Clause 9e) requires the location of the fracture to be recorded. The four different fracture locations include – “in the pipe or the socket, between the windings or at the interface”. These fracture locations are to be reported as per the requirements in Clause 11 of ISO 13954.

ISO 21751:2011 *Plastic pipes and fittings – Decohesion test of electrofusion assemblies – Strip-bend test is another test* method referenced in AS/NZS 4129 which looks at the same modes of fracture. At the time of writing, ISO 21751 is under revision but has not yet been republished.

Test method ASTM F1055–2016 *Electrofusion Type Polyethylene Fittings for Outside Diameter Controlled Polyethylene and Crosslinked Polyethylene (PEX) Pipe and Tubing* is similar to ISO 13954, although there are differences in the applied rate and direction of loading. ASTM F1055 is more explicit in describing the fracture modes than ISO 13954 and what constitutes failure of the weld. In particular, tearing between the winding is a passing result. Refer to the bullet points below:

- Ductile failure between wires is described as a Passing Result (refer to figure A2.4 of ASTM F1055).
- Ductile failure in the pipe is described as a Passing Result (refer to Figure A2.3 of ASTM F1055).
- Brittle separation of fusion zone is described as a Failing Result (refer to Figure A2.5 of ASTM F1055).

Note: The ISO 13954 test method requires the tensile testing machine to indicate the “separating force for documentation”, although only the maximum breaking load has to be recorded and reported. Recording the load vs. extension curve can be a useful aid in the fracture mode assessment and it is recommended this information be kept as part of the test record.

6.0 ASSESSMENT OF FRACTURE MODES

When assessing destructive weld test coupons to ISO 13954, the location of the fracture is to be recorded in accordance with Clause 9e), including the type of fracture (i.e., in the pipe, in the socket, between the windings or at the interface). Examples of brittle failure in the fusion plane and ductile failure in the wire plane are illustrated in a series of photographs in Table 1 of the Standard together with details as to how to calculate the percentage brittle failure.

Tearing between the windings or fracture through the pipe or fitting wall is evidence that fusion between the interfaces has been achieved, indicating a pass result.

Typical types of fractures are as follows:

DUCTILE FRACTURE IN THE PIPE WALL

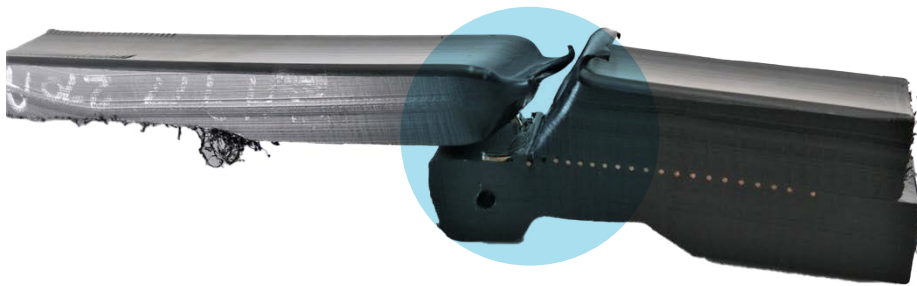


Figure 3 – shows ductile fracture of the pipe wall has occurred. **This is a Pass result.**

DUCTILE FRACTURE IN THE FITTING SOCKET

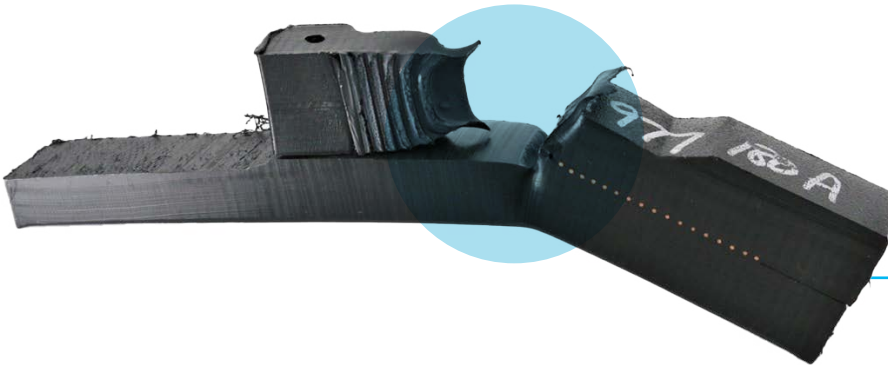


Figure 4 – Figure 4 shows partial separation through the windings, followed by ductile fracture through the fitting socket wall. **This is a Pass result.**

DUCTILE FRACTURE IN THE PLANE OF THE WINDINGS

It must be recognised that not all ductile surfaces will look the same. Nor will the fracture surface necessarily look the same across the sample width. Edge effects, slight misalignment can alter the appearance of the surface.

Where tearing between the wires occurs, it is expected that some differences in surface appearance will be apparent. The geometry of the test piece changes during the test, the stress field differs between the edge zones and the body of the test piece, strain rate will vary.

This means that the observed level of ductility can vary from obvious gross tearing of the PE material (gross ductility) to very minor tearing of the PE material known as micro-ductility. Confirmation of **micro-ductility** will require the use of low magnification light microscopy (refer to Appendix B Micro-ductility)

Tearing between the windings over a length of at least 66.7% of the fusion zone demonstrates satisfactory fusion of the PE across the interface.



Figure 5 – shows ductile fracture (tearing) of the PE between the windings. Stress whitening is apparent across most of the fusion zone surfaces, with some gross ductility near the edges towards the centre of the test piece. **This is a Pass result.**

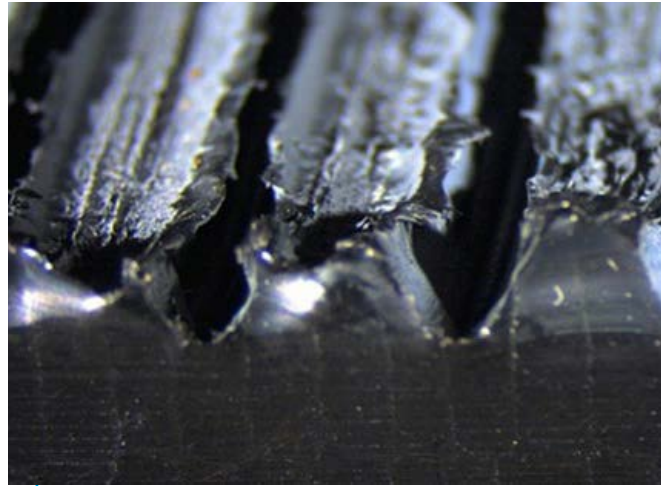


Figure 6 – shows the side view of ductile fracture with tearing of the PE occurring between the windings of the heating wire. The wires are no longer encapsulated in the PE and have been dislodged. Ductile tearing is present in the fracture zone.

BRITTLE FRACTURE AT THE FUSION INTERFACE

Where separation occurs at the interface between the pipe and fitting surfaces, an assessment needs to be made as to whether there is evidence of ductility. A brittle fracture, indicating absence of fusion, will be flat and featureless. Stress whitening at the fracture surface is indicative of fusion at the interface as is gross ductility.

In accordance with AS/NZS 4129, voids represent an absence of fusion and are treated as regions of brittle fracture. Examples of voids are shown in Figure 13. Heating wires dislodged during destructive testing are not to be classified as voids.



Figure 7 – shows a large area of brittle separation at the interface of the pipe and fitting surfaces. **This is a Fail result.**



Figure 8



Figure 9

Figures 8 and 9 shows a side view of brittle fracture occurring at the fitting pipe interface with embedded heating wires remaining encapsulated in the PE. **Figure 9 shows a Fail result.**



Figure 10 – shows brittle separation at the interface by the featureless surface. **This is a Fail result.**

MIXED MODE FAILURES

Mixed mode failure is defined as multiple fractographic features present along the entire length of the fusion interface, i.e., ductile tearing or yielding in the plane of the wires, brittle lack of fusion and voids.

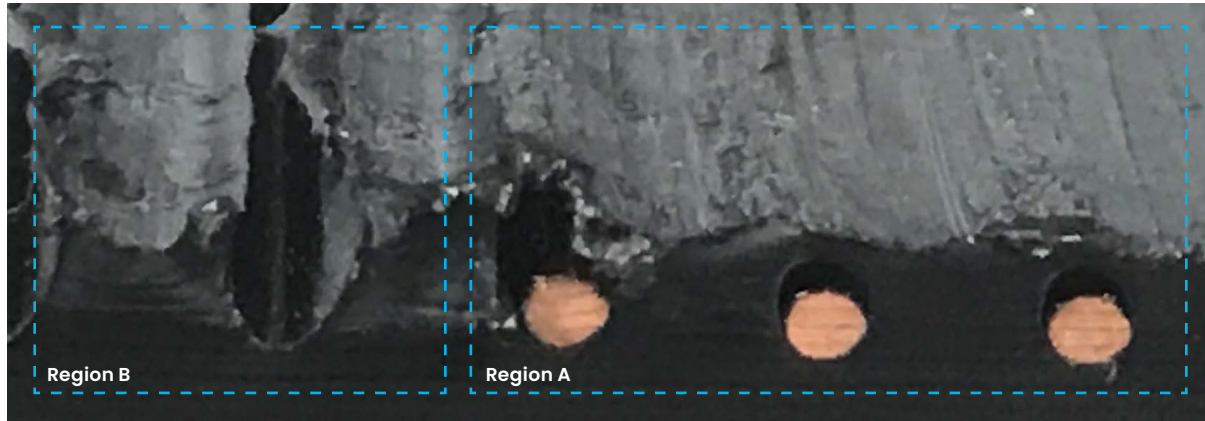


Figure 11 – is a close-up, side view of the EF fitting weld that matches the pipe side shown in Figure 12 below.

Region A: Brittle fracture in the weld interface zone between the pipe and EF coupling and above the wire plane. Some minor ductility exhibited around the 2nd and third wires from the right. No corresponding wire imprints formed on the pipe side.

Region B: Ductile yielding of the material between the wire locations.

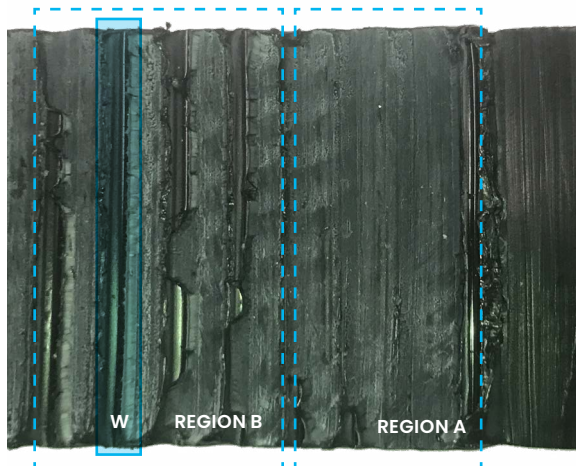


Figure 12 – is a close-up of the pipe fusion interface exhibiting mixed mode failures – ductile and brittle / lack of fusion zone.

Region A: Pipe side, essentially a featureless surface showing brittle fracture in the weld interface zone, wire imprints from the EF fitting have not formed.

Region B: Pipe side ductile yielding of the PE material between the well-defined wire imprints (W).

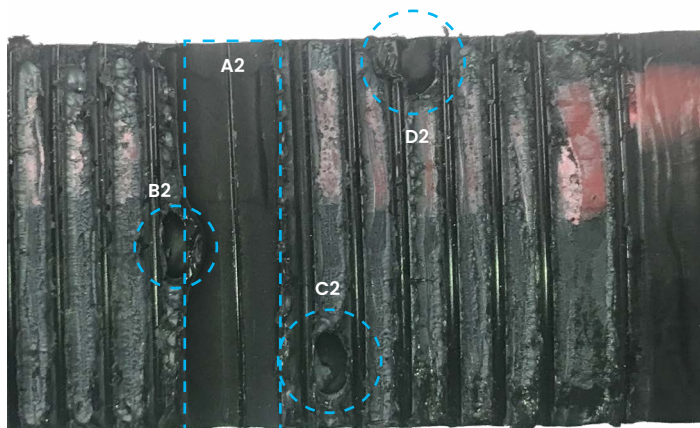


Figure 13 – shows the pipe side of an EF weld exhibiting a large void (A2) that transverses the entire width of the test sample plus three small voids (B2, C2 & D2). Remaining area exhibits ductile yielding in the plane of wires.

Section 6.1 provides a full fractographic assessment of the fracture zone and calculation of percentage brittle decohesion region for **Figure 11 & 12** and **Figure 13**.

6.1 MIXED MODE – PERCENTAGE BRITTLE DECOHESION ASSESSMENT AND CALCULATION EXAMPLES

The following calculation examples are based on figures 11 & 12 and figure 13 of a peel decohesion test as per ISO 13954 on DN250 EF weld assemblies. They are evaluated in terms of their fractographic features and the resultant percentage brittle decohesion.

Mixed mode fractographic features – percentage brittle decohesion calculation

EXAMPLE 1 – ASSESSMENT FIGURES 11 & 12



Figure E1.1: Electrofusion coupler – plan view of full fracture zone based on the close-up image shown in Figure 11.

- A1 and C1 are brittle fracture regions within the full fracture zone. These regions show a smooth featureless surface and wires remain in place and covered. Fracture in these regions is at the interface between the pipe and fitting, indicating lack of fusion.
- B1 is a ductile fracture region, with material yielding occurring through the plane of the wires.

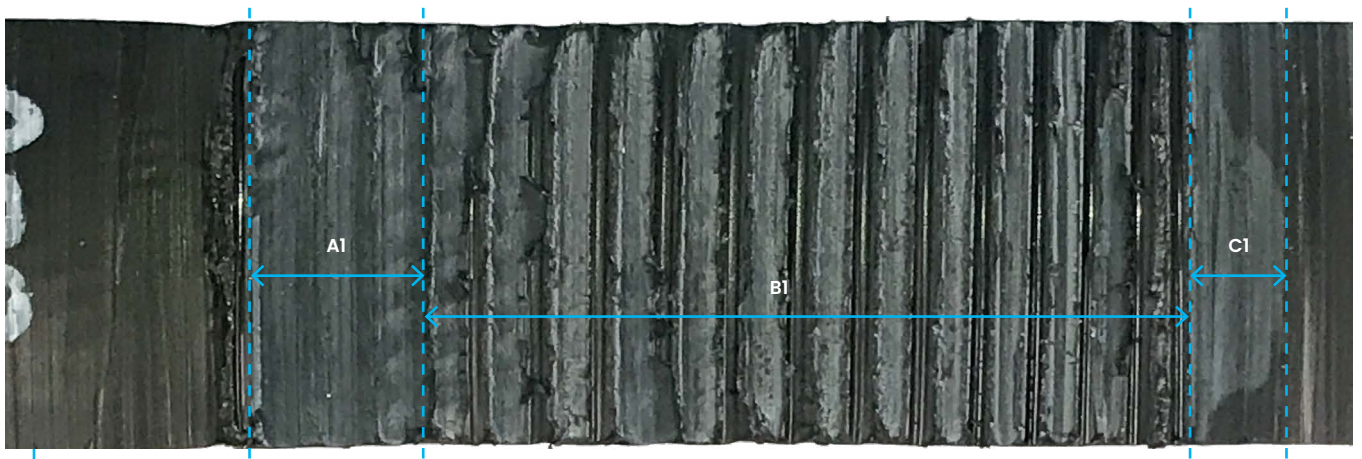


Figure E1.2: Pipe side – plan view of the full fracture zone based on the close-up image shown in Figure 12.

- A1 and C1 are brittle fracture regions within the full fracture zone. These regions show a smooth featureless surface and no wire imprints visible.
- B1 is a ductile fracture region where wire imprints are clearly visible.

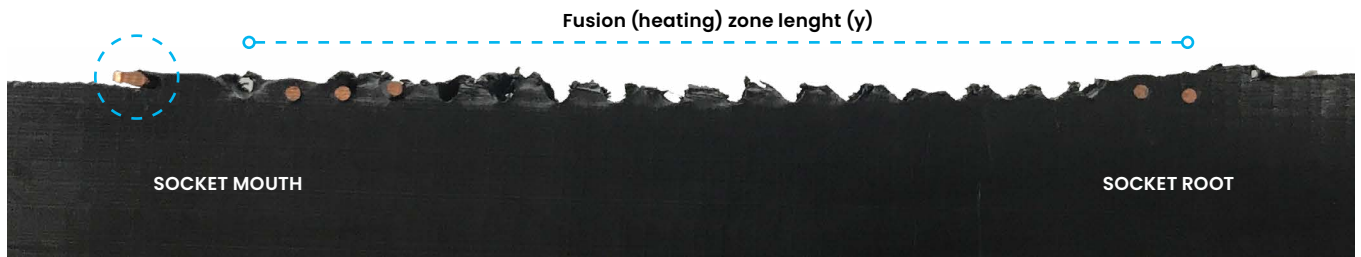


Figure E1.3: Electrofusion coupler – side view of the full fracture zone based on the close-up image shown in Figure 12.

Figure E1.3 shows the fusion heating zone length that is used in the calculation of the percentage brittle decohesion. This length should be measured prior to destructive testing and is typically defined as the length where there is even spacing between the wires. The blue circled wire is at a greater off set versus the evenly spaced wires in the heating zone. The end of the wire connects to the EF fitting terminal and does not form part of the fusion zone. In many cases the fusion zone length is specified in EF fitting manufacturers product data sheets and should be used where available.

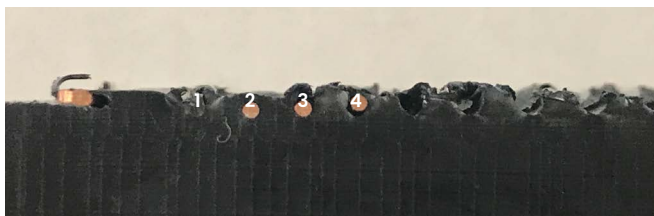


Figure E1.3.1: Close-up of EF coupler socket mouth showing brittle fracture at the fusion interface from heating wire locations 2 through to 4.

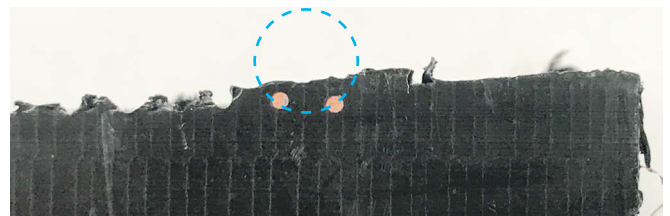


Figure E1.3.2: Close-up of EF coupler socket root showing brittle fracture at the fusion interface for the last two wires (circled above).

Calculating the percentage brittle decohesion

This calculation focuses on taking the measurements of the EF coupler side of the weld using Figures E1.2 and E1.3.

Measurements:

Fusion (heating) zone length (y) = 68.7mm
 Brittle fracture length (A1) = 11mm
 Brittle fracture length (C1) = 6mm

Calculations as per principles described in ISO 13954:

$d2$ (maximum brittle fracture length)
 $= (A1 + C1) = 17\text{mm}$

Percentage brittle decohesion:
 $CC = \frac{d2}{y} \times 100 = (17/68.7) \times 100 = \mathbf{24.7\%}$

Result:

$Cc = 24.7\%$ which is $< 33\%$ brittle.

This is a pass result.

EXAMPLE 2 – TREATMENT OF VOIDS, ASSESSMENT OF FIGURE 13

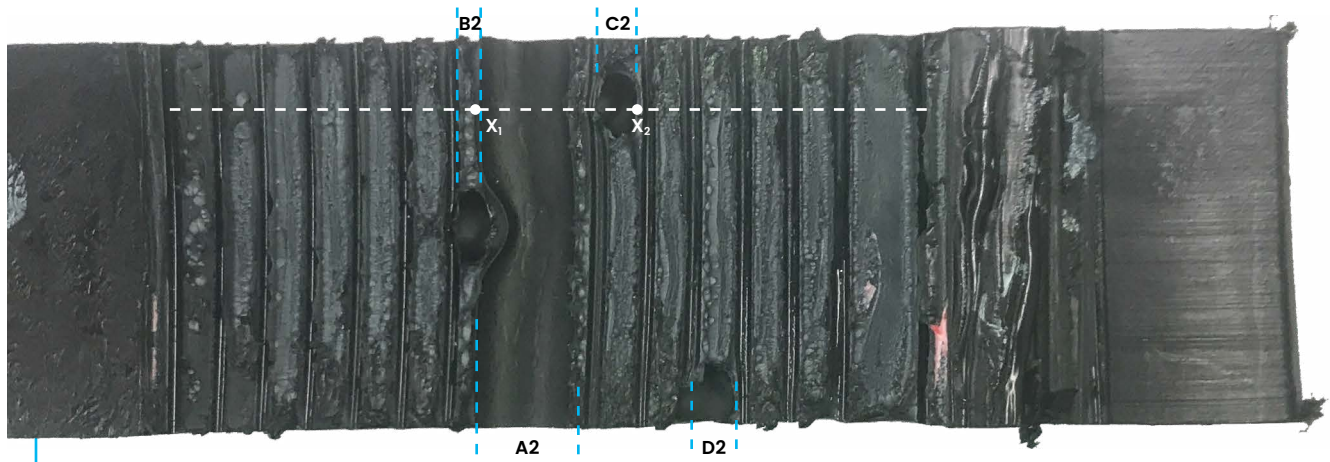


Figure E2.1: Electrofusion coupler – plan view of the full fracture zone matching the close-up image of the pipe side shown in Figure 13.

- This shows the EF coupling side with the matching large void (A2) that transverse the entire width of the test sample, plus the three smaller voids (B2, C2 & D2).
- Voids B2, C2 and D2 are equal to the width of each individual fusion region (spacing between wires). It should be noted that these spacings are not always equal. The wire location width is not to be treated as part of the void zone.
- It should not be assumed that small voids extend across the full width of the test piece.
- Only voids in the same plane shall be measured and used in the calculation of the brittle decohesion zone. This is achieved by drawing a straight line through the fracture zone that presents the worst case in terms of accumulated voids and brittle fracture, represented by the line that runs through points X_1 to X_2 in figure E2.1 above. The summation of the individual void lengths ($A2 + C2$) between X_1 and X_2 is the brittle fracture length.
- The remaining area exhibits ductile yielding in the plane of wires.

Note: Void treatment rationale is based on two potential failure modes in EF joints:

- i) Shear strength reduction – a small void will not cause the same reduction in shear strength of a joint as a void that extends across the full width of the test piece.
- ii) Leak path creation – several off-set voids will have a lesser effect on the length of the leak path in the joint than would the same number of voids extending across the full width of the test piece.



Figure E2.2: Electrofusion coupler – side view of the full fracture zone.

This shows the fusion heating zone length that is used in the calculation of the percentage brittle decohesion.

Calculating the percentage brittle decohesion

This calculation focuses on taking the measurements of the EF coupler side of the weld using Figures E2.1 and E2.2.

Measurements:

Fusion (heating) zone length (y) = 64mm
 Void length (A2) = 7.5mm
 Void length (B2) = 1.7mm
 Void length (C2) = 2.8mm
 Void length (D2) = 2.6mm

Calculations as per ISO 13954:

d2 (maximum brittle fracture length)
 = (A2 + C2) = 10.3mm

Percentage brittle decohesion:
 $Cc = \frac{d2}{y} \times 100 = \frac{10.3}{64} \times 100 = \mathbf{16.1\%}$

Result

$Cc = 16.1\%$ which is < 33% brittle.

This is a pass result.

7.0 TECHNICAL REFERENCES

[J. Bowman, T. Medhurst and R. Portas, Procedures for the quantifying the strength of electrofusion joints, Plastics Pipes VIII, Kongingshof, The Netherlands, September 1992.](#)

[J. Bowman, Stages in the development of the strength of electrofusion joints, ANTEC 1992](#)

[J. Bowman, A review of the electrofusion joining process for polyethylene pipe systems, Poly. Eng. And Sci., Vol. 37, No. 4, p674, 1997.](#)

[J. Bowman, The assessment of the strength of electrofusion joints, Twelfth plastic fuel gas pipe symposium, Boston, 1991.](#)

8.0 STANDARDS REFERENCES

- AS/NZS 4129:2020 *Fittings for polyethylene (PE) pipes for pressure applications*
- AS/NZS 4130 *Polyethylene pipes for pressure applications*
- ASTM F1055–2016 (2022) *Electrofusion Type Polyethylene Fittings for Outside Diameter Controlled Polyethylene and Crosslinked Polyethylene (PEX) Pipe and Tubing*
- ISO 13954 - *Plastics pipes and fittings – Peel decohesion test for polyethylene (PE) electrofusion assemblies of nominal outside diameter greater than or equal to 90 mm*
- ISO 21751:2011 *Plastic pipes and fittings – Decohesion test of electrofusion assemblies – Strip-bend test*

APPENDIX A

DEFINITIONS

Term	Definition
Failure	Any break of the test piece which is visible to the naked eye.
Ductile, ductility	Fractures characterised by material tearing and plastic deformation such as stretching and elongation.
Ductile failure	Failure showing plastic deformation prior to separation. Note 1: Ductile failures are characterized by the presence of gross yielding. Note 2: Micro-ductile failure often occurs with stress-whitening which may require further investigation using an optical microscope.
Tearing	Breaking apart a material through the application of force without the aid of a cutting tool.
Yielding	Behaviour of a material stressed beyond the elastic limit and exhibiting permanent, inelastic deformation.
Brittle failure	Failure showing no plastic deformation in the fusion plane after separation Note 1: Brittle failure is characterized by smooth failure surface(s) without any fibrils. Note 2: Brittle failure occurs instantaneously at relatively low stresses and strains (low failure energy).
Brittle	Fracture of any component with little or no macroscopically visible plastic deformation. Brittle fracture usually involves little energy absorption.
Cohesion	Fusion across the pipe-fittings interface so the PE material behaves as one.
Decohesion	Separation of the pipe and fitting at the weld interface or in the plane of the electrofusion wires.
Rupture	Rupture, or ductile rupture describes the ultimate failure of ductile materials loaded in tension.
Fracture	Separation of two halves of the test specimen under the action of stress.
Failure Mode	Pattern of failure defined by distinctive features of the deformed shape after failure; manner in which the failure occurs i.e., brittle, ductile or mixed mode.
Fractography, fractographic	Analysis and characterisation of features generated on the fracture surface of a test specimen or engineering component.
Destructive test	Test method resulting in damage or destruction of the sample / specimen being tested.
Fusion	A process for bonding a polymer by heating and melting two polymer surfaces and pressing the surfaces together. This forms a common over-structure, created by co-crystallisation of the macromolecules beyond the weld interface.
Stress whitening	The colour change associated with cold drawing of a semi-crystalline polymer. It is thought to result from a combination of micro void and craze formation when the applied local stress exceeds the yield stress.
Fusion Interface	The pipe and fitting contact faces that are joined together in the heat fusion process.
Void	A hole or empty space that is formed within the fusion zone.
Lack of fusion	Absence of intermolecular diffusion, entanglement, and co-crystallisation at the fusion interface between two surfaces.
Micro-ductility	Ductile plastic deformation across a fusion interface observed through low magnification (5 – 40x) light microscopy.

APPENDIX B

MICRO DUCTILITY

Assessment of micro ductility is made easier by being able to clearly identify brittle fracture both macroscopically and microscopically and is shown in the examples below.

Brittle fracture zones at the weld interface between the pipe and EF fitting will display little or no macroscopically visible plastic deformation, tearing or elongation. This is also the case in microscopic examination of a brittle fracture surface at the weld interface at low magnifications, for example Figures B.1 and B.2 at 6.4x and 16x magnification respectively.

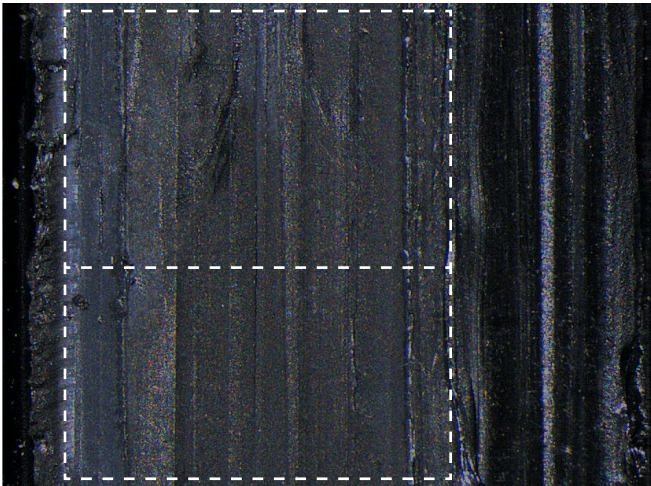


Figure B.1 – Brittle fracture zone on the EF fitting side of the weld at 6.4x magnification.

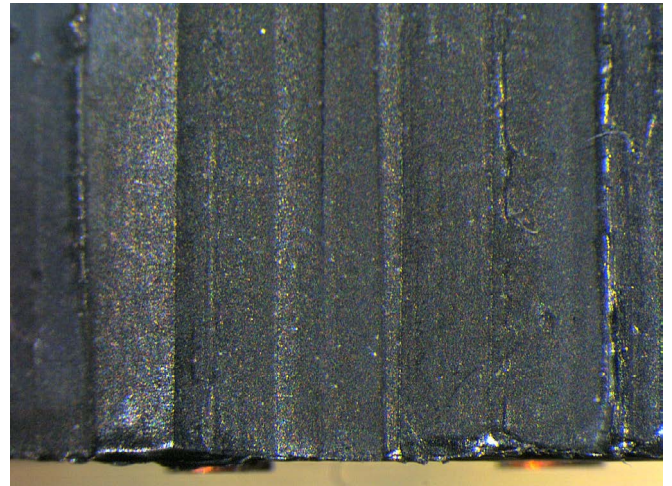


Figure B.2 – Brittle fracture zone on the EF fitting side of the weld at 16x magnification (bottom section of figure B.1).

Ductile fracture is characterized by material tearing and plastic deformation. Gross plastic deformation is easily detected by visual (macroscopic) examination. However, **micro ductility** may also be present and requires low (5–40x) magnification microscopic examination to confirm its presence. An example of micro ductility when viewed at 6.4x, 16x and 40x magnification through a stereo microscope is given in figures B.3, B.4 and B.5.

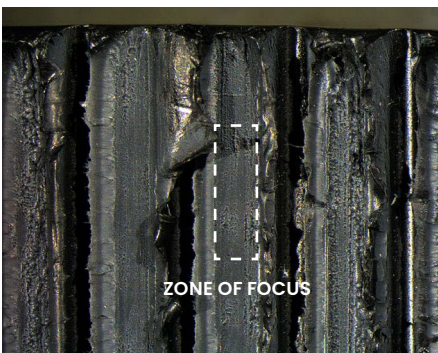


Figure B.3 – Micro ductility present in the fracture zone – viewed at 6.4x magnification. Note gross plastic deformation is present on each vertical side of the zone of focus.

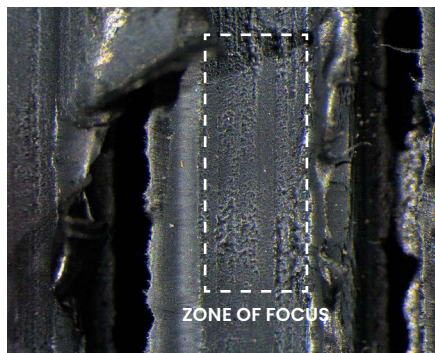


Figure B.4 – Micro ductility present in the fracture zone – viewed at 16x magnification.

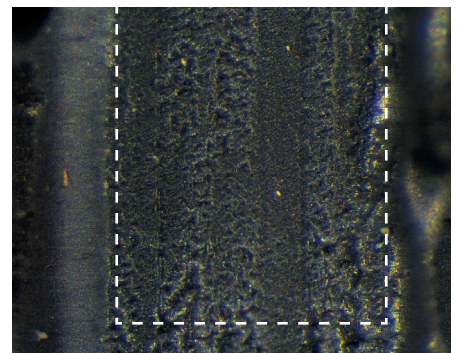


Figure B.5 – Micro ductility – viewed at 40x magnification.



PIPA

PLASTICS INDUSTRY
PIPE ASSOCIATION
OF AUSTRALIA LIMITED

PO Box 957 North Lakes Q 4509

E plasticspipe@pipa.com.au

P +61 (0) 459 919 437

pipa.com.au

Disclaimer

In formulating this guideline PIPA has relied upon the advice of its members and, where appropriate, independent testing.

Notwithstanding, users of the guidelines are advised to seek their own independent advice and, where appropriate, to conduct their own testing and assessment of matters contained in the guidelines, and to not rely solely on the guidelines in relation to any matter that may risk loss or damage.

PIPA gives no warranty concerning the correctness or accuracy of the information, opinions and recommendations contained in the guidelines. Users of the guidelines are advised that their reliance on any matter contained in the guidelines is at their own risk.